

Influence of Lanthanides on the Phase Composition of Portland cement Clinker Accessed by Thermodynamic Modelling

Ana Rita Damasceno Costa¹, Luanne Bastos de Britto Barbosa¹, Ana Paula Kirchheim², Jardel Pereira Gonçalves^{1,3}

¹Federal University of Bahia (UFBA), Polytechnic School
Salvador, Brazil, 40210-630
rita.damasceno@ufba.br; luanneb@ufba.br

²Federal University of Rio Grande do Sul (UFRGS), Department of Civil Engineering
Porto Alegre, Brazil, 90035-190
anapaula.k@ufrgs.br

³Federal University of Bahia (UFBA), Interdisciplinary Centre of Energy and Environment (CIENAM)
Salvador, Brazil, 40170-115
jardelpg@ufba.br

Abstract - The development of sustainable production has motivated using alternative raw materials in Portland cement manufacture. Co-processing industrial by-products containing impurities can change the stability of the clinker phases. Several studies have explored the effect of minor elements in the clinkering process. However, the effect of lanthanides remains unclear. This class of elements has been scarcely investigated due to its limited content in conventional alternative materials. Nevertheless, the increasing co-processing of by-products from the oil industry containing lanthanides demands further investigations on the effects of these elements. Furthermore, using alternative raw materials demands extensive experimental programs and investing time and financial resources. In this context, this study uses thermodynamic modelling to evaluate the effect of lanthanides on Portland clinker production. Systems containing La, Ce, Eu, Gd, Pr, and Nd as oxides in up to 10 wt.% of clinker raw meal processed at 1200 and 1400 °C were simulated. Thermodynamic calculations were based on the Gibbs energy minimisation method and performed in the FactSage software. La, Pr, Eu, Nd, and Gd improved the clinker C₃S content. This effect was more significant for up to 3 wt.% of added dopant. These elements stabilised C₂(A,F) rather than C₃(A,F), suggesting a possible application in manufacturing high-ferrite and sulphate-resistant cements. Ce₂O₃ promoted notably different behaviour on phase assemblage, decreased the C₃S development, and depleted C₂(A,F). The cubic perovskite was the main solid phase

incorporating the lanthanides, forming LaAlO₃, NdAlO₃, PrAlO₃, EuAlO₃, or GdAlO₃. According to thermodynamic modelling, the co-processing of raw materials containing lanthanides can be environmentally safe since the emission of polluting gases containing impurities was negligible even when co-processing 10 wt.% of lanthanide oxide in the clinker raw meal.

Keywords: Clinker, Cement, Thermodynamic modelling, Dopants, Lanthanides.

© Copyright 2023 Authors - This is an Open Access article published under the Creative Commons Attribution License terms (<http://creativecommons.org/licenses/by/3.0>). Unrestricted use, distribution, and reproduction in any medium are permitted, provided the original work is properly cited.

1. Introduction

The cement industry is responsible for high environmental impacts. The exploitation of natural raw materials can lead to resource depletion, deforestation, soil destabilisation, and other harmful effects [1]. In this scenario, the co-processing of industrial by-products in cement manufacture reduces the extraction of natural sources, promotes proper waste disposal, and often improves sustainability in production [2]. However, it is

noteworthy that these by-products contain elements besides those essential for the Portland cement composition (Ca, Si, Fe, Al, O), which can alter the phase development during production.

Several studies have explored the co-processing of alternative raw materials in Portland clinker production [3]–[6]. This approach can improve manufacturing sustainability and product properties by optimizing clinker composition and burnability [7]. On the other hand, the presence of potentially contaminating elements can promote limitations in the production process on an industrial scale, change the stability of clinker phases, emission of polluting gases during clinkering, and contaminate the environment by the leaching of hazardous compounds [3], [8]. In this sense, the co-processing of alternative raw materials should always be associated with studying the effects of impurities in the clinker phase assemblage and the environmental risk assessment.

The solidification of metals in clinker was reported as altered by the added content, industrial technology, processing time, and other impurities [9], [10]. The presence of non-metals can reduce the stabilisation temperature of Ca_2SiO_4 polymorphs, altering the hydraulicity of the cement and the mechanical properties of the pastes [11]. Several studies have investigated the effect of alkaline and transition metals on the stability of aluminates and their polymorphs [12], [13]. Although extensive research has been carried out on the effect of metals and non-metals on clinker, the presence of lanthanides needs further investigation.

The limited number of research on the influence of lanthanides in clinker production was justified by the restricted contents of these elements in ordinary alternative materials (< 0.1 wt.%) [14]. However, the increasing volume of waste from the oil industry being co-processed in cement kilns in recent years demands new investigations addressing the effect of these impurities on clinkering and gas emissions. As an example, lanthanum and cerium oxides comprised up to 5.1 and 1.6 wt.% of the spent fluid catalytic cracking catalyst (SFCC), respectively [15], [16]. SFCC was co-processed in previous investigations to replace bauxite in clinker production [4]–[6]. Nevertheless, the findings examine neither the effects of lanthanides on the clinker mineralogical composition nor their emission potential during clinkering.

Understanding the action mechanisms of lanthanides can be technologically challenging. It demands the execution of an extensive and complex

experimental program, consuming financial resources, and time. In this sense, thermodynamic modelling is a useful solution. It applies the Gibbs energy minimisation principle to estimate the clinker composition throughout manufacturing. Previous investigations have established it as an accurate tool for phase determination [17], [18]. Modelling allows for optimizing experimental approaches by analysing the effect of dopants on the composition of solid, liquid, and gaseous phases along clinkering [19]–[21]. It was applied to evaluate the effect of FeO, K_2O , MgO, Na_2O , SiO_2 , SO_3 , and TiO_2 [22]–[24]. However, further investigations could broaden the understanding of the effect of lanthanides incorporated in clinker raw meals due to the co-processing of alternative raw materials.

In this sense, this study applies thermodynamic modelling to investigate the influence of lanthanides on Portland clinker production. The effects of impurities on the stability of silicates and aluminates were investigated, in addition to the formation of new compounds and the polluting gases emission.

2. Methodology

2.1. Thermodynamic modelling

Thermodynamic modelling was adopted to estimate the mineral composition of the clinkers produced in the theoretical study. The software FactSage version 8.2 were applied to simulations. It contains optimised model parameters for the Gibbs free energy minimisation of solution phases to clinker equilibrium calculations [19]. Thermodynamic databases for gaseous components (FactPS) and oxides in solid, liquid, and solution phases (FToxid) were used for calculating the phase assemblage during production [19], [20]. The system pressure was fixed at 1 atm and the firing temperature was 1400 °C. As input data, the composition of clinker raw meal for an ordinary Portland cement (OPC) (69.5% CaO, 22.0% SiO_2 , 5.0% Al_2O_3 , and 3.5% Fe_2O_3) was used. The lanthanides were added individually as oxides (La_2O_3 , Ce_2O_3 , Eu_2O_3 , Gd_2O_3 , Pr_2O_3 , and Nd_2O_3) in up to 10 wt.% of the raw meal in 0.5 wt.% increments. The influence of dopants on the phase assemblage was evaluated at 1200, 1300, and 1400 °C during clinkering. The processing was applied using the software Equilibrium module and adopting the entire set of products available in the system. Calcium silicates are quantified as Ca_3SiO_5 (C_3S) and Ca_2SiO_4 (C_2S). Thermodynamic modelling using FactSage considers solid solutions of calcium aluminium ferrites, such as

$\text{Ca}_2(\text{Al,Fe})_2\text{O}_5$ ($\text{C}_2(\text{A,F})$) and $\text{Ca}_3(\text{Al,Fe})_2\text{O}_6$ ($\text{C}_3(\text{A,F})$) [17], [19], [20]. Where (Al,Fe) means Al and Fe are variable in the structure. The modelled solid solution $\text{C}_2(\text{A,F})$ is mainly associated with the OPC ferrite content, $\text{Ca}_2(\text{Al}_x\text{Fe}_{1-x})_2\text{O}_5$, often named as C_4AF [25]. The tricalcium aluminate or C_3A ($\text{Ca}_3\text{Al}_2\text{O}_6$) content is included in the $\text{C}_3(\text{A,F})$ solid solution, and the complementary content corresponds to intermediate phases in the development of C_4AF [20]. Thermodynamic modelling allowed quantifying other solids, including free calcium oxide (CaO) and new compounds formed from the chemical combination of lanthanides (LaAlO_3 , NdAlO_3 , PrAlO_3 , EuAlO_3 , GdAlO_3 , $\text{Gd}_4\text{Al}_2\text{O}_9$, CeO_2 , Ce_6O_{11} , and $\text{Ce}_{18}\text{O}_{31}$) [19]. The calculated liquid phase corresponded to the melt phase content formed during clinkering. The melt fraction is mainly developed through the melting of aluminates ($\text{Ca}(\text{Al,Fe})_2\text{O}_4$, $\text{Ca}_2(\text{Al,Fe})_2\text{O}_5$ and $\text{Ca}_3(\text{Al,Fe})_2\text{O}_6$) from 1250 °C, reaching their maximum at the final clinkering temperature and then resolidifying during clinker cooling [14], [25].

FactSage is the software with the broadest database for thermodynamic modelling of reactions at high temperatures [26]. The accuracy of thermodynamic calculations has been reported in previous investigations that simulated the clinkering process. The results were experimentally validated in the following applications: Influence of bauxite residue co-processed in Fe-rich calciumsulfoaluminate-ferrite clinker (CSAF) [27]; Effects of co-processing impurities, including MgO, ZnO, Cr_2O_3 , and NiO in different zones of an industrial rotary kiln [28]; Influence of the kiln atmosphere on the quality of clinker produced on an industrial scale [21]; Effects of impurities containing phosphorus on the stability of silicates in clinker [20]; Valorisation of blast furnace slag in clinker production [29]; Effect of mineralising agents (CaF_2 , AlF_3 , MgSiF_6 , Na_2SiF_6 , CaCl_2 , ZnO, and CaSO_4) on clinker production [24]; Influence of the gradual substitution of Al_2O_3 with Fe_2O_3 in the raw material of an ordinary Portland clinker [30]. In this regard, all these applications have demonstrated that thermodynamic modelling results in better agreement with the phase composition of real clinkers compared to estimations from Bogue equations. These findings demonstrate the value of thermochemical calculations as an important tool for expanding the understanding of clinker production.

This study focused on analysing the effect of lanthanides during heating on clinker production (1200, 1300, and 1400 °C). The emission of compounds containing lanthanides was identified by quantifying

gaseous phases during clinkering at 1400 °C through thermodynamic calculations on FactSage.

3. Results and discussions

3. 1. Composition of an Ordinary Portland Clinker (OPC) during heating

Table 1 presents the composition of an OPC at different temperatures to illustrate the phase evolution in an undoped system. Tricalcium silicate (C_3S) is the main phase of OPC, responsible for the early-age compressive strength of hydrated cement [2]. It is formed during clinkering after 1250 °C and obtained through the reaction between dicalcium silicate (C_2S) and calcium oxide (CaO) [14]. C_2S is generally the first silicate formed in clinkering. This compound increases the later-age compressive strength of cementitious materials [2]. Modelling using FactSage identifies its gamma ($T < 735$ °C), alpha prime (735~1435 °C), and alpha ($T > 1435$ °C) polymorphs [25]. If the system has free CaO, it combines with C_2S at about 1280 °C to form C_3S [14]. This reaction is verified in Table 1, where CaO is depleted at 1300 and 1400 °C as C_3S increases.

During heating, the proportion of $\text{C}_3(\text{A,F})$ tends to be higher than $\text{C}_2(\text{A,F})$. However, previous investigations have shown that this ratio tends to reverse during cooling [17]. The reason is the combination of CaO dissolved in the melt phase with C_2S forming additional C_3S [14]. Thereby, Ca availability is reduced for aluminates, promoting the formation of $\text{C}_2(\text{A,F})$ instead of $\text{C}_3(\text{A,F})$. In this sense, although the modelled OPC has a high content of $\text{C}_3(\text{A,F})$ during heating at 1200 and 1400 °C, the system tends predominantly to form $\text{C}_2(\text{A,F})$ during cooling [17]. At 1400 °C, $\text{C}_2(\text{A,F})$ and $\text{C}_3(\text{A,F})$ reached the melting point and then were converted to the melt phase.

Table 1. Predicted ordinary Portland clinker composition (wt.%) during clinkering at 1200, 1300 and 1400 °C.

Composition	Phase	1200 °C	1300 °C	1400 °C
Ca_3SiO_5	C_3S	0.00	68.64	76.26
$\text{Ca}_2\text{SiO}_4 \alpha'$	$\text{C}_2\text{S} \alpha'$	63.07	11.29	3.39
$\text{Ca}_2(\text{Al,Fe})_2\text{O}_5$	$\text{C}_2(\text{A,F})$	2.36	1.59	0.00
$\text{Ca}_3(\text{Al,Fe})_2\text{O}_6$	$\text{C}_3(\text{A,F})$	17.54	18.48	0.00
CaO	CaO	17.03	0.00	0.00
Melt	Melt	0.00	0.00	20.35

3. 2. Composition of lanthanide-doped clinkers at 1200 °C

Previous investigations established that the lanthanides would act similarly on the stability of the clinker phases due to their comparable atomic characteristics [14]. However, thermodynamic modelling indicated that Ce promotes notably different behaviours on the phase evolution during clinkering. On the other hand, La, Pr, Eu, Gd and Nd indeed have similar trends. Figure 1 shows the effect of lanthanide type and content on the phase assemblage during clinkering at 1200 °C. Figure 1a presents the data for La e as a representation of Pr, Eu, Gd, and Nd for simplification purposes, as the effect of these other lanthanides was similar.

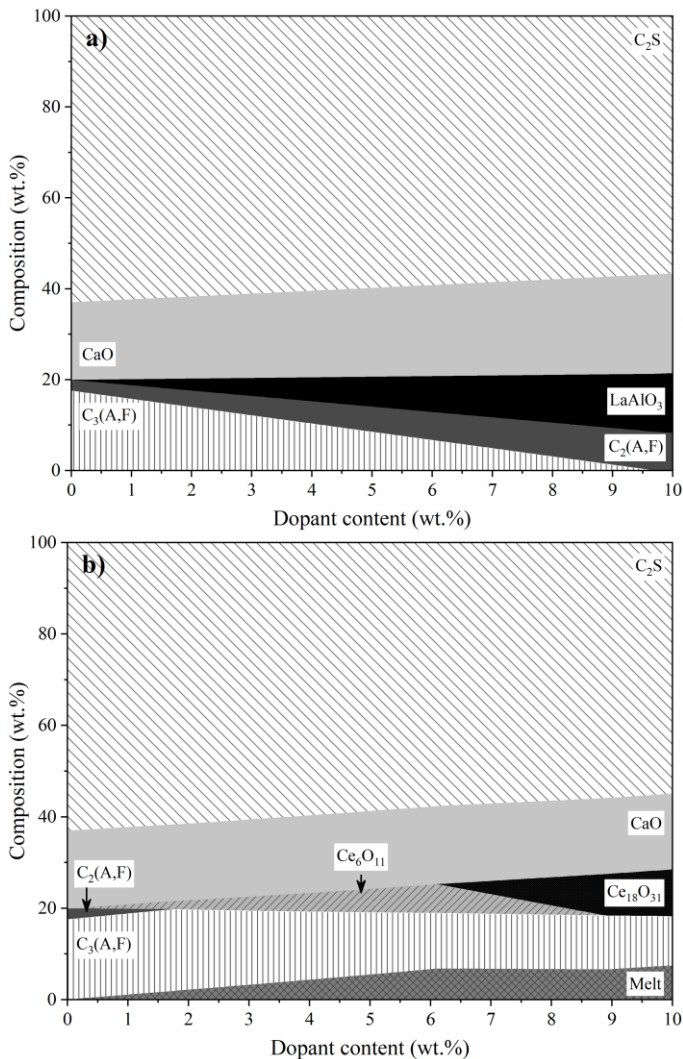


Figure 1. Composition modelled for clinker produced at 1200 °C and doped with up to 10 wt.% lanthanum (a) and cerium (b) oxides.

La, Pr, Eu, Gd, and Nd stabilised $C_2(A,F)$ rather than $C_3(A,F)$. Clinkers start from 2.4 wt.% $C_2(AF)$ and reach up to 8.2 wt.% when the dopant content is maximised (Figure 2a). For $C_3(AF)$, the content varies from 17.5 wt.% to values below 1.1 wt.%. This behaviour indicates that the presence of lanthanides promotes the formation of clinkers rich in C_4AF . This characteristic is particularly promising for producing high ferrite clinker, in which the C_3A content is limited, to guarantee the requirements of resistance to abrasion and attack by sulphates [31]. The evolution of calcium aluminium-ferrite according to the Ce_2O_3 content stands out among the analysed lanthanides (Figure 2b). Ce destabilised $C_2(A,F)$ by depleting it when 1.8 wt.% Ce_2O_3 was added. $C_3(A,F)$ is partially reduced as the dopant increases. Ce acted as a flux, lowering the melting point, and gradually increasing the melt phase content up to 6.1% Ce_2O_3 .

Co-processing impurities in cement kilns promote the formation of compounds beyond those commonly found in OPC. Figure 1 presents the new solid phases of the modelled systems with up to 10 wt.% of dopants. La, Pr, Eu, Gd, and Nd were incorporated as cubic perovskite containing Al and O. The doped systems indicated the formation of $LaAlO_3$, $PrAlO_3$, $EuAlO_3$, $GdAlO_3$, and $NdAlO_3$ with increasing values as the dopant content is increased. Previous investigations reported the formation of cubic lanthanum aluminate at temperatures above 540 °C [32], which can be pseudo-cubic or rhombohedral under industrial conditions [33]. Although the modelled structure of $PrAlO_3$ was cubic, this compound has the highest number of crystalline structure transitions among rare earth perovskites [34]. $NdAlO_3$ and $GdAlO_3$ were classified as materials with high optical conductivity, applicable in producing optical amplifiers and solar panels [35], [36]. For Gd, doping above 8 wt.% resulted in the destabilisation of $GdAlO_3$ and the formation of $Gd_4Al_2O_9$. This phase was synthesised in previous research by processing Gd_2O_3 and Al_2O_3 at temperatures ranging between 1400 and 1700 °C [37]. $Gd_4Al_2O_9$ is classified as an enhancer of the mechanical properties of ceramic materials, including the toughness and fracture strength of brittle ceramics [38].

Although the thermodynamic database includes the cerium aluminate perovskite [19], the simulations did not identify it (Figure 1b). Previous studies have shown that the combining potential of Ce in structures containing aluminium depends on several factors, including processing in a reducing atmosphere, pressure of O_2 in the atmosphere, proportion of other impurities

in the reagents, and heat treatment conditions [39]–[41]. Thermodynamic calculations showed Ce_2O_3 did not react with Al_2O_3 in the clinker raw meal, remaining in its pure crystalline forms and varying as the dopant content increased (CeO_2 , Ce_6O_{11} , and $\text{Ce}_{18}\text{O}_{31}$). Additional experimental investigations are necessary to understand the Ce action mechanism during clinkering and the formation of new solid compounds containing this element.

3. 3. Composition of lanthanide-doped clinkers at 1400 °C

The phase evolution at 1400 °C as a function of the dopant increment shows that La, Pr, Eu, Gd, and Nd enhanced C_3S formation (Figure 2a).

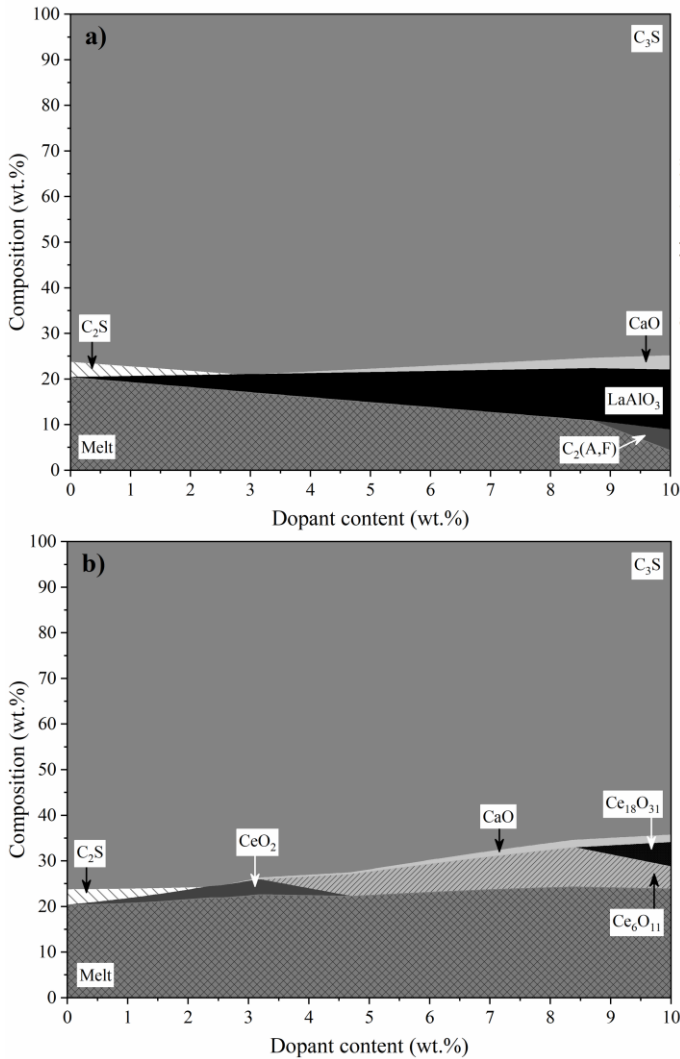


Figure 2. Composition modelled for clinker produced at 1400 °C and doped with up to 10 wt.% lanthanum (a) and cerium (b) oxides.

Up to 3% dopant, the C_3S content shows a positive development rate, starting from 76.3 wt.% (0% dopant) and reaching up to 79.0 wt.% (3% dopant). This behaviour is related to the C_2S destabilisation, which starts from 3.4 wt.% and is depleted in this range (Figure 2a). In this sense, lanthanides improve the clinker composition, increasing the C_3S content by optimizing the reaction between C_2S and CaO dissolved in the melt phase. A similar effect was observed in experimental samples doped with Praseodymium (Pr) [42].

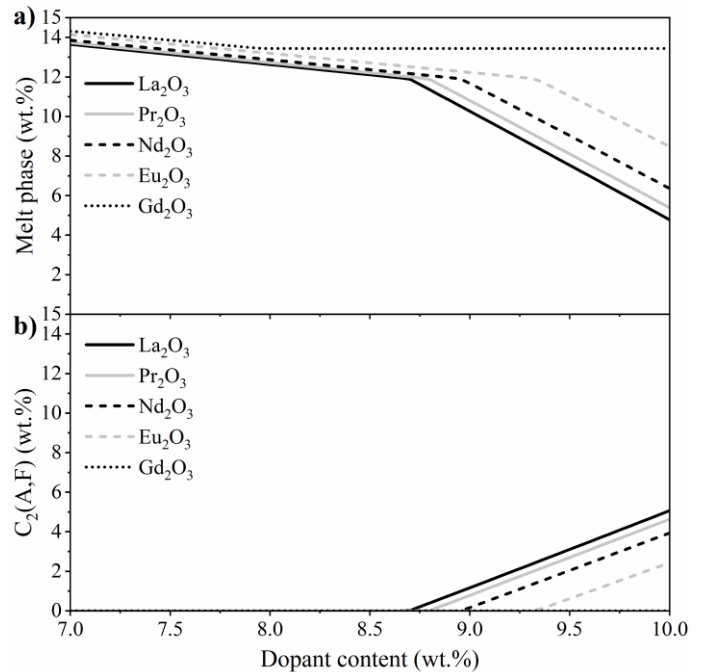


Figure 3. Recrystallisation zone of $\text{C}_2(\text{A},\text{F})$ modelled for clinker produced at 1400 °C and doped with lanthanide oxides. a) Melt phase content and b) $\text{C}_2(\text{A},\text{F})$ content.

After 3 wt.% dopant, the C_3S content decreased gradually, reaching 74.9 wt.% when 10 wt.% dopant was added. However, it is noteworthy that this percentage was improved, since the system produced 98% of the reference C_3S amount (instead of 90%) even with 10 wt.% substitution of raw materials by lanthanides. In this range, the depletion of C_2S limits the C_3S growth. After 8 wt.% dopant, part of the melt phase recrystallised as $\text{C}_2(\text{A},\text{F})$. The results do not fully explain the recrystallisation occurring at high lanthanide contents. There are no lanthanides in the melt phase. Furthermore, resolidification occurs at different levels for each dopant, starting at 8.7 wt.% for La_2O_3 , followed by Pr_2O_3 (8.8 wt.%), Nd_2O_3 (9.0 wt.%), and Eu_2O_3 (9.3 wt.%) (Figure 3). In this sense, high levels of this oxides (8~10%) increased the melting point of the clinker raw

meal, promoting a considerably lower content of the melt phase at 1400 °C.

Cerium promoted discrepant effects compared to the analysed lanthanides (Figure 2b). Although the system started with the same C₂S content (3.4 wt.%) and it was depleted in advance (occurring at 2.3 wt.% Ce₂O₃), the C₃S content declined for increasing dopant levels. It reached 64.3 wt.% when 10 wt.% Ce₂O₃ was added, i.e., 84% of the calculated C₃S for OPC (76.3 wt.%). This decrease may be related to the SiO₂ destabilisation. In this sense, C₃S tends to decompose into solid CaO and molten SiO₂. The increased free CaO and melt in the C₃S depletion regions evidenced this behaviour (Figure 2b).

3. 4. Emissions

Table 2 quantifies the emission of potentially polluting gases containing lanthanides accessed by thermodynamic modelling.

Table 2. Emission of compounds containing lanthanides simulated by thermodynamic modelling of the clinkering of raw meals containing 10 wt.% lanthanide oxide (1400 °C).

Lanthanide	Compound	Emission (µg/t of clinker)
La	La	5.7 10 ⁻²²
	La ₂	9.8 10 ⁻⁴⁸
	LaO	1.0 10 ⁻⁷
	La ₂ O	8.1 10 ⁻³¹
	La ₂ O ₂	8.6 10 ⁻¹⁸
Pr	Pr	2.6 10 ⁻²⁰
	PrO	1.7 10 ⁻⁶
Eu	Eu	2.6 10 ⁻¹²
	EuO	8.1 10 ⁻⁷
	Eu ₂ O	1.4 10 ⁻²²
Nd	Eu ₂ O ₂	4.6 10 ⁻¹⁴
	Nd	1.7 10 ⁻¹⁹
	NdO	1.1 10 ⁻⁷
Gd	NdO ₂	43.16
	Gd	5.8 10 ⁻²¹

All dopants showed negligible emission levels. Nd had the highest emission potential. However, the volatilised phase (NdO₂) was in the order of micrograms per ton of clinker produced, a value easily mitigated by the protection infrastructure of industrial kilns. On the other hand, the modelling did not detect the emission of gases containing Ce. This behaviour was attributed to the stability of its oxides as solid phases, as discussed in the

previous section. For La, Pr, and Eu, the emission tended to higher values when the oxidation state of these elements was 2⁺. According to the modelling, the emission of polluting gases containing lanthanides does not promote environmental risk since the emissions were approximately zero even when co-processing 10 wt.% of lanthanide oxide in the clinker raw meal.

4. Conclusions

According to the results of this study, the following conclusions can be drawn:

La, Pr, Eu, and Nd showed similar effects, enhancing the C₃S content. This effect occurred on a larger scale for up to 3 wt.% of added dopant, when C₂S is depleted in the clinker. Ce promoted notably different behaviours on phase assemblage, decreasing the C₃S development depending on the dopant content.

Increasing lanthanide content generally stabilised C₂(A,F) rather than C₃(A,F), suggesting that these elements may be applicable to produce high-ferrite and sulphate-resistant cements.

Co-processing lanthanides promoted the formation of new compounds, mainly the cubic perovskite containing Al and O (LaAlO₃, NdAlO₃, PrAlO₃, EuAlO₃, and GdAlO₃), with increasing values as the dopant content is increased. However, Ce₂O₃ remained in its pure crystalline forms, varying as the dopant content increased (CeO₂, Ce₆O₁₁, and Ce₁₈O₃₁).

The emission of polluting gases containing lanthanides was low even when co-processing 10 wt.% of lanthanide oxide in the clinker raw meal. However, it needs to be compared with the limits of the environmental regulations of each location. Furthermore, investigations are needed to understand how impurities could be immobilised in the cementitious material.

Acknowledgements

The authors express their sincere appreciation to the Bahia State Research Support Foundation (FAPESB, Brazil - Grant number 0289/2020 to A.R.D.C.) and the Coordination for the Improvement of Higher Education Personnel (CAPES, Brazil - Grant number 88887.608021/2021-00 to L.B.B.B.) for their financial support. J.P.G. and A.P.K. gratefully acknowledge the National Council for Scientific and Technological Development (CNPq, Brazil) and the Foundation for Research Support of the State of Rio Grande do Sul (FAPERGS, Brazil).

References

- [1] K. S. Kumar, “Environmental impact assessment of a Proposed Bauxite mining using Rapid Impact Assessment Matrix Method”, *International Journal of Applied Environmental Sciences*, vol. 5, no 1, p. 29–38, 2010, [Online]. Available: <http://www.ripublication.com/ijaes.htm>
- [2] S. P. Deolalkar, *Designing Green Cement Plants*. Oxford: Butterworth-Heinemann (Elsevier), 2016. doi: 10.1016/c2014-0-00783-6.
- [3] A. A. Bogush, J. A. Stegemann, Q. Zhou, Z. Wang, B. Zhang, T. Zhang, W. Zhang, and J. Wie, “Co-processing of raw and washed air pollution control residues from energy-from-waste facilities in the cement kiln”, *Journal of Cleaner Production*, vol. 254, maio 2020, doi: 10.1016/j.jclepro.2019.119924.
- [4] S. R. C. Matos, P. R. de Matos, J. S. Andrade Neto, C. E. M. Campos, A. P. Kirchheim, e J. P. Gonçalves, “Synthesis and hydration of ye’elinite-containing cement (YCC) produced with spent fluid catalytic cracking catalyst”, *Construction and Building Materials*, vol. 359, dez. 2022, doi: 10.1016/j.conbuildmat.2022.129364.
- [5] K. L. Lin, K. W. Lo, M. J. Hung, T. W. Cheng, e Y. M. Chang, “Recycling of spent catalyst and waste sludge from industry to substitute raw materials in the preparation of Portland cement clinker”, *Sustainable Environment Research*, vol. 27, p. 251–257, set. 2017, doi: 10.1016/j.serj.2017.05.001.
- [6] H. Al-Dhamri e K. Melghit, “Use of alumina spent catalyst and RFCC wastes from petroleum refinery to substitute bauxite in the preparation of Portland clinker”, *Journal of Hazardous Materials*, vol. 179, p. 852–859, jul. 2010, doi: 10.1016/j.jhazmat.2010.03.083.
- [7] D. N. Huntzinger e T. D. Eatmon, “A life-cycle assessment of Portland cement manufacturing: comparing the traditional process with alternative technologies”, *Journal of Cleaner Production*, vol. 17, p. 668–675, maio 2009, doi: 10.1016/j.jclepro.2008.04.007.
- [8] M.-Y. Lee, Y.-J. Kim, D.-G. Hwang, Y.-Y. Kang, S.-K. Shin, e T.-W. Jeon, “Potential risk of exposure to heavy metals from co-processing of secondary wastes in the Republic of Korea”, *Journal of Environmental Management*, vol. 286, maio 2021, doi: 10.1016/j.jenvman.2021.112164.
- [9] L. Blois e A. Lay-Ekuakille, “Environmental impacts from atmospheric emission of heavy metals: A case study of a cement plant”, *Measurement: Sensors*, vol. 18, dez. 2021, doi: 10.1016/j.measen.2021.100313.
- [10] L. Wang, X. Huang, X. Li, X. Bi, D. Yan, W. Hu, C. J. Lim, and J. R. Grace, “Simulation of heavy metals behaviour during Co-processing of fly ash from municipal solid waste incineration with cement raw meal in a rotary kiln”, *Waste Management*, vol. 144, p. 246–254, maio 2022, doi: 10.1016/j.wasman.2022.03.031.
- [11] S. Saidani, A. Smith, Y. el Hafiane, e L. ben Tahar, “Role of dopants (B, P and S) on the stabilization of β -Ca₂SiO₄”, *Journal of the European Ceramic Society*, vol. 41, p. 880–891, jan. 2021, doi: 10.1016/j.jeurceramsoc.2020.07.037.
- [12] A. B. Ghazi, A. Jamshidi-Zanjani, e H. Nejati, “Clinkerisation of copper tailings to replace Portland cement in concrete construction”, *Journal of Building Engineering*, vol. 51, jul. 2022, doi: 10.1016/j.jobe.2022.104275.
- [13] J. Zhu, Y. Chen, L. Zhang, B. Guo, G. Fan, X. Guan, and R. Zhao, “Revealing the doping mechanism of barium in sulfoaluminate cement clinker phases”, *Journal of Cleaner Production*, vol. 295, maio 2021, doi: 10.1016/j.jclepro.2021.126405.
- [14] J. I. Bhatti, F. M. Miller, e S. H. Kosmatka, *Innovations in Portland cement manufacturing*, 2o ed. Skokie: Portland Cement Association, 2011. [Online]. Disponível em: www.cement.org
- [15] E. Restrepo, F. Vargas, E. López, e C. Baudín, “The potential of La-containing spent catalysts from fluid catalytic cracking as feedstock of mullite based refractories”, *Journal of the European Ceramic Society*, vol. 40, p. 6162–6170, dez. 2020, doi: 10.1016/j.jeurceramsoc.2020.04.051.
- [16] Y. Xue, X. Wei, H. Zhao, T. Wang, e Y. Xiao, “Interaction of spent FCC catalyst and asphalt binder: Rheological properties, emission of VOCs and immobilization of metals”, *Journal of Cleaner Production*, vol. 259, jun. 2020, doi: 10.1016/j.jclepro.2020.120830.
- [17] T. Hanein, F. P. Glasser, e M. N. Bannerman, “Thermodynamic data for cement clinkering”, *Cement and Concrete Research*, vol. 132, jun. 2020, doi: 10.1016/j.cemconres.2020.106043.
- [18] D. Ariño Montoya, N. Pistofidis, G. Giannakopoulos, R. I. Iacobescu, M. S. Katsiotis, e Y. Pontikes, “Revisiting the iron-rich ‘ordinary Portland cement’ towards valorisation of wastes: study of Fe-to-Al ratio on the clinker production and the hydration reaction”, *Materials and Structures*, vol. 54, no 30, 2021, doi: 10.1617/s11527-020-01601-w.

- [19] C.W. Bale, E. Bélisle, P. Chartrand, S. A. Decterov, G. Eriksson, A. E. Gheribi, K. Hack, I.-H. Jung, Y.-B. Kang, J. Melançon, A. D. Pelton, S. Petersen, C. Robelin, J. Sangster, P. Spencer, and M.-A. V. Ende, “Reprint of: FactSage thermochemical software and databases, 2010–2016”, *CALPHAD*, vol. 55, p. 1–19, 2016, doi: 10.1016/j.calphad.2016.07.004.
- [20] B. Hökfors, D. Boström, E. Viggh, e R. Backman, “On the phase chemistry of Portland cement clinker”, *Advances in Cement Research*, vol. 27, no 1, p. 50–60, jan. 2015, doi: 10.1680/adcr.13.00071.
- [21] B. Hökfors, M. Eriksson, e E. Viggh, “Modelling the cement process and cement clinker quality”, *Advances in Cement Research*, vol. 26, no 6, p. 311–318, nov. 2014, doi: 10.1680/adcr.13.00050.
- [22] M. Cantaluppi, N. Marinoni, F. Cella, A. Bravo, F. Cámara, G. Borghini, and W. Kagan, “An insight on the effect of sodium and silicon on microstructure and crystallography of high alumina cements”, *Cement and Concrete Research*, vol. 148, out. 2021, doi: 10.1016/j.cemconres.2021.106533.
- [23] S. Cheng, M. Shevchenko, P. C. Hayes, e E. Jak, “Experimental phase equilibria studies in the FeO-Fe₂O₃-CaO-SiO₂ system and the subsystems CaO-SiO₂, FeO-Fe₂O₃-SiO₂ in air”, *Metallurgical and Materials Transactions B: Process Metallurgy and Materials Processing Science*, vol. 52, p. 1891–1914, jun. 2021, doi: 10.1007/s11663-021-02159-w.
- [24] A. Tazuddin, H. Aiyer, e A. Chatterjee, “Thermodynamic simulation in evaluating the role of minor oxides and mineralizers in Portland cement clinker phase formation”, *SN Applied Sciences*, vol. 2, out. 2020, doi: 10.1007/s42452-020-03548-7.
- [25] P. Hewlett e M. Liska, *Lea’s chemistry of cement and concrete*, 5o ed. Oxford: Butterworth-Heinemann (Elsevier), 2017. doi: 10.1016/C2013-0-19325-7.
- [26] I. H. Jung e M. A. Van Ende, “Computational thermodynamic calculations: FactSage from CALPHAD thermodynamic database to virtual process simulation”, *Metallurgical and Materials Transactions B: Process Metallurgy and Materials Processing Science*, vol. 51, no 5, p. 1851–1874, out. 2020, doi: 10.1007/s11663-020-01908-7.
- [27] T. Hertel, A. Van den Bulck, S. Onisei, P. P. Sivakumar, e Y. Pontikes, “Boosting the use of bauxite residue (red mud) in cement - Production of an Fe-rich calciumsulfoaluminate-ferrite clinker and characterisation of the hydration”, *Cement and Concrete Research*, vol. 145, jul. 2021, doi: 10.1016/j.cemconres.2021.106463.
- [28] D. Thompson e B. B. Argent, “Modelling trace and alkali mobilisation in the rotary cement kiln”, *Transactions of the Institutions of Mining and Metallurgy, Section C: Mineral Processing and Extractive Metallurgy*, vol. 116, no 2, p. 115–122, jun. 2007, doi: 10.1179/174328507X163805.
- [29] K. Prasad, C. Srishilan, A. K. Shukla, e M. Kaza, “Thermodynamic assessment and experimental validation of clinker formation from blast furnace slag through lime addition”, *Ceramics International*, vol. 44, no 16, p. 19434–19441, nov. 2018, doi: 10.1016/j.ceramint.2018.07.180.
- [30] D. A. Montoya, N. Pistofidis, G. Giannakopoulos, R. I. Iacobescu, M. S. Katsiotis, e Y. Pontikes, “Revisiting the iron-rich ‘ordinary Portland cement’ towards valorisation of wastes: study of Fe-to-Al ratio on the clinker production and the hydration reaction”, *Materials and Structures*, vol. 54, no 30, fev. 2021, doi: 10.1617/s11527-020-01601-w.
- [31] X. Huang, S. Hu, F. Wang, L. Yang, M. Rao, Y. Mu, and C. Wang, “The effect of supplementary cementitious materials on the permeability of chloride in steam cured high-ferrite Portland cement concrete”, *Construction and Building Materials*, vol. 197, p. 99–106, fev. 2019, doi: 10.1016/j.conbuildmat.2018.11.107.
- [32] S. A. Hayward, F. D. Morrison, S. A. T. Redfern, E. K. H. Salje, J. F. Scott, K. S. Knight, S. Tarantino, A. M. Glazer, V. Shuvaeva, P. Daniel, M. Zhang, and M. A. Carpenter, “Transformation processes in LaAlO₃: Neutron diffraction, dielectric, thermal, optical, and Raman studies”, *Physical Review B: Condensed matter and materials physics*, vol. 72, ago. 2005, doi: 10.1103/PhysRevB.72.054110.
- [33] M. Rizwan, S. Gul, T. Iqbal, U. Mushtaq, M. H. Farooq, M. Farman, R. Bibi, and M. Ijaz, “A review on perovskite lanthanum aluminate (LaAlO₃), its properties and applications”, *Materials Research Express*, vol. 6, no 11, set. 2019, doi: 10.1088/2053-1591/ab4629.
- [34] V. Shrivastava e R. Nagarajan, “Iron substitution in PrAlO₃ perovskite leading to structural transformation and multiferroicity”, *Ceramics International*, vol. 47, no 16, p. 22957–22964, ago. 2021, doi: 10.1016/j.ceramint.2021.05.009.
- [35] M. Harilal, V. M. Nair, P. R. S. Wariar, K. P. Padmasree, M. M. Yusoff, e R. Jose, “Electrical and optical properties of NdAlO₃ synthesized by an optimized combustion process”, *Materials Characterization*, vol. 90, p. 7–12, 2014, doi: 10.1016/j.matchar.2014.01.011.

- [36] G. R. Remya, S. Solomon, J. K. Thomas, e A. John, “Optical and dielectric properties of nano GdAlO₃”, *em Materials Today: Proceedings*, Elsevier Ltd, 2015, p. 1012–1016. doi: 10.1016/j.matpr.2015.06.027.
- [37] M. Shimada, H. Yamane, H. Takizawa, e T. Endo, “Phase transformation of Gd₄Al₂O₉ at high temperature”, *Key Engineering Materials*, vol. 132–136, p. 647–650, abr. 1997, doi: 10.4028/www.scientific.net/kem.132-136.647.
- [38] M. Shimada, T. Sakamoto, e H. Yamane, “Preparation and high temperature strength of Gd₄Al₂O₉/MgO composites”, *Ceramic Materials and Components for Engines*, p. 469–470, 2001, doi: 10.1002/9783527612765.ch79.
- [39] X. Zheng, J. Qi, Y. Zheng, e C. Liu, “Synthesis and characterization of CeAlO₃ via solid state method”, *Journal of Solid State Chemistry*, vol. 312, ago. 2022, doi: 10.1016/j.jssc.2022.123220.
- [40] F. Czerwinski, “Cerium in aluminum alloys”, *Journal of Materials Science*, vol. 55, no 1, p. 24–72, jan. 2020, doi: 10.1007/s10853-019-03892-z.
- [41] D. Weiss, “Improved high-temperature aluminum alloys containing cerium”, *Journal of Materials Engineering and Performance*, vol. 28, no 4, p. 1903–1908, abr. 2019, doi: 10.1007/s11665-019-3884-2.
- [42] H. Congyun, Z. Mingfei, Z. Meixiang, L. Shizong, C. Yuankui, e M. Baoguo, “Effect of minor elements on silicate cement clinker”, *Journal of Wuhan University of Technology - Materials Science Edition*, vol. 20, no 3, p. 116–118, 2005, doi: 10.1007/BF02835044.